



钢铁之家

www.steels.org.cn

全球钢号百科!

Global Steel Grade Encyclopedia



涵盖的行业或国家与地区类别



国际材料与试验协会

GJB

国家军用标准



动力机械工程师协会

EU

前欧洲标准化

AISI

美国钢铁学会



德国工业标准

AMS

航空航天材料规范



国际标准

JASO

日本汽车标准组织

EN

欧洲标准

JB

中国机械行业标准

UNS

统一编号系统

UNI

意大利标准



美国机械工程师协会

SS

瑞典标准



国家标准



日本工业标准

Cryodur 2842

90MnCrV8

C 0.90 Si 0.20 Mn 2.00 Cr 0.40 V 0.10

Steel properties

Good cutting edge retention, dimensionally stable during heat treatment.

Standards

AISI O2 AFNOR 90MV8

Physical properties

Coefficient of thermal expansion

at °C	20 – 100	20 – 200	20 – 300	20 – 400	20 – 500	20 – 600	20 – 700
10 ⁻⁶ m/(m · K)	12.2	13.2	13.8	14.3	14.7	15.0	15.3

Thermal conductivity

at °C	20	350	700
W/(m · K)	33.0	32.0	31.3

Applications

Tool steel for universal use, cutting and stamping tools for sheet up to 6 mm thickness, thread-cutting tools, reamers, gauges, measuring tools, plastic moulds, shear blades, guide strips and ejector pins.

Heat treatment

Soft annealing °C
680 – 720

Cooling
Furnace

Hardness HB
max. 220

Stress-relief annealing °C
approx. 650

Cooling
Furnace

Hardening °C
790 – 820


Quenching
Oil or
saltbath, 180 – 220 °C

Hardness after quenching HRC
64

Tempering °C
HRC

100	200	300	400	500	600
63	60	56	50	42	38

Time-temperature-transformation diagram

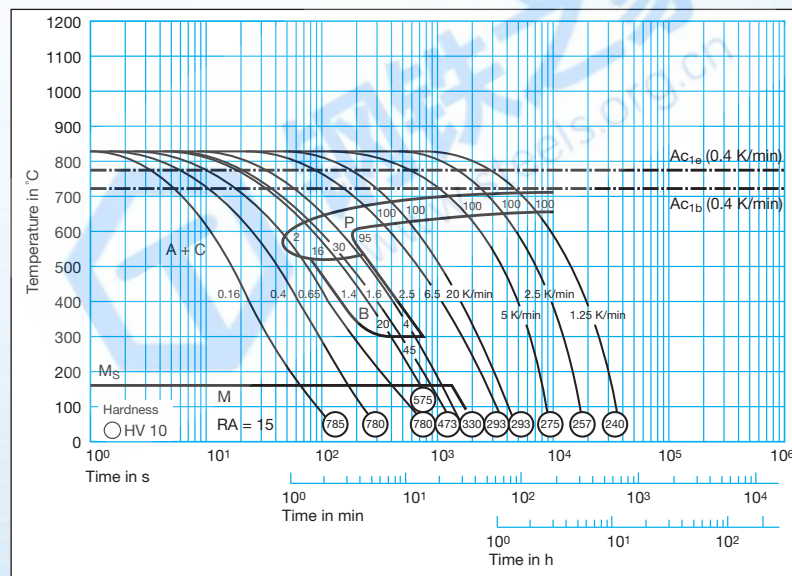

Tempering diagram

